

检测报告 编号: SDHL2206011762FT 日期:2022年07月05日 页码: 第1页共6页

新駿貿易有限公司 東莞市厚街鎮家具大道金盈大厦 1 樓

样品描述 : 西班牙 TITAN 165 度内置阻尼快装门铰

购买商型号/货号 : SAH-216T

以上样品及信息由客户提供及确认,SGS不承担证实客户提供信息的准确性、适当性、可靠性和(或)完整性责任。

收样日期 : 2022年06月11日

检测日期 : 2022年06月16日至2022年07月04日

执行检测 : 按申请者要求进行检测

测试结果总结

编号	测试要求	测试结果	备注		
1	参照 BS EN 14074:2004 条款 6.3.3 的铰链耐久性测试	符合	/		
2	ISO 9227:2017	9级	/		
详细的测试结果请看附页					

通标标准技术服务有限公司顺德分公司 授权代表签署

学北岳

梁兆禹 授权签字人

此报告结果仅对测试样品负责





Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions/Terms

| 15,1⁴ Building European Industrial Part, No.1 Stunde South Road, Washa Section, Dallarg Town, Shunde, Foshar, Guangdong, China 528333 t (86-757)22805888 f (86-757)22805858 www.sgsgroup.com.cn
中国・广东・佛山市原徳区大良街道办事处五沙原和南路号欧洲工业园一号厂房首层 邮编: 528333 t (86-757)22805888 f (86-757)22805858 e sgs.china@sgs.com



检测报告

编号: SDHL2206011762FT

日期:2022年07月05日

页码:第2页共6页

检测和结果

检测依据第1部分:

参照 BS EN 14074:2004 条款 6.3.3 的铰链耐久性测试。

样品数量:

1对。如果想了解更多的样品信息和图片,请查看下述的样品信息页。

检测项目方法和要求	检测结果
6.3.3 铰链门耐久性测试 把2kg重的砝码,均等分布连接在门的垂直中心的两侧。 打开门最大到165°,然后完全关闭,重复这样的操作共40000次。在测试过程中,在完全打 开状态时,不能有力对其限位装置作用。操作的速率最大为每分钟6次。 如果铰链具有自开或自闭装置的,则每个循环其也要正确地运行。 测试前后,铰链及其零件应满足其功能要求且没有任何损坏。	符合

备注:

- 1. 测试门的尺寸是 700 mm 高 x 600 mm 宽 x 19 mm 厚, 其重量为 5.4kg;
- 2. 开门角度 165°,循环次数 40000 次和总承重 7.4kg 由申请者指定。



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention:To check the authenticity of testing / inspection report & certificate, please contact us at telephone:(86-755) 8307 1443, or email: CN.Doccheck@sgs.com

[146-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-757102006080] ** (186-75710

| 16,1⁶ Building European Industrial Part, No.1 Shurshe South Read, Wasta Section, Dallarg Town, Shurshe, Frishan, Grangdong, China 528333 t (86-757)22805888 f (86-757)22805858 www.sgs.group.com.cn
中国・广东・佛山市原徳区大良街道办事处五沙原和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757)22805888 f (86-757)22805858 e sgs.china@sgs.com



检测报告 编号: SDHL2206011762FT 日期:2022年07月05日 页码: 第3页共6页

检测依据据第2部分:

ISO 9227:2017 人造气氛腐蚀测试 — 盐雾测试。

样品数量:

1件(样品#1)。如果想了解更多的样品信息和图片,请查看下述的样品信息页。

1. 综合信息:

- 测试方法: 中性盐喷雾测试

- 盐液浓度: 50 g/l ± 5 g/l

- 盐溶液酸碱度(PH): 6.5~7.2

- 沉降率: (1.5 ± 0.5)ml/(80cm²•h)

- 测试时间: 72 小时

- 盐雾箱温度: (35 ± 2)°C

2. 外观评级 (参考 ISO 10289

2. 外观评级 (参考 ISO 10289:1999)						
1.	外观评级是基于 ISO 10289:1999,该	评级 (外观或保护评级)	检测样表面腐蚀面积 A (%)			
标准只是一个方法标准,检测结果的符合和不符合的评价取决于客户的接收标准。 2. 外观评级是基于 0 到 10 级共分为 11 个等级,0 级表示抗腐蚀能力差,10		10	无腐蚀			
		9	0 < A ≤ 0.1			
		8	0.1 < A ≤ 0.25			
		7	0.25 < A ≤ 0.5			
		6	0.5 < A ≤ 1.0			
	级表示抗腐蚀能力好。	5	1.0 < A ≤ 2.5			
	, , , , , , , , , , , , , , , , , , ,	4	2.5 < A ≤ 5.0			
		3	5.0 < A ≤ 10			
		2	10 < A ≤ 25			
		1	25 < A ≤ 50			
		0	50 < A			
3. 检测结果						
样品编号.		外观评级				
# 1		9级				

备注:

- 本报告是编号为 SDHL2206011761FT 英文检测报告的中文译本,如有歧义,以英文版本为准;
- 2. 检测报告仅用于客户科研、教学、内部质量控制、产品研发等目的,仅供内部参考;
- 3. 请翻到下一页获取样品信息和图片。



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx. Attention is drawn to the limitation of liability, indemnification and jurisdiction is successed defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention:To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@gs.com

| 作。「Paiding European Industrial Part, Na.1 Strunte South Read, Wusta Section, Dallaring Tomn, Shunde, Foshar, Gazangdong, China 528333 tt (86-757)22805888 ft (86-757)22805888 www.sgs.group.com.cn 中国・广东・佛山市原徳区大良街道办事处五沙展和南路1号欧洲工业园一号厂房首层 邮编:528333 tt (86-757)22805888 ft (86-757)22805888 e sgs.china@sgs.com



检测报告

编号: SDHL2206011762FT

日期:2022年07月05日

页码:第4页共6页

样品信息和图片

重量: 200.58 g/件


尺寸: Φ35 mm

其他尺寸: /

样品图片





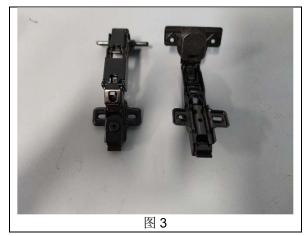






| 15, 「Buiding European Industrial Part, Na.1 Sturtle South Read, Wistra Section, Dallarg Tom, Sturtle Forbia, Guargdong, China 528333 t (86-757)22805888 f (86-757)22805888 www.sgs.group.com.cn 中国・广东・佛山市原徳区大良街道办事处五沙厩和南路1号欧洲工业园一号厂房首层 邮编:528333 t (86-757)22805888 f (86-757)22805888 e sgs.china@sgs.com





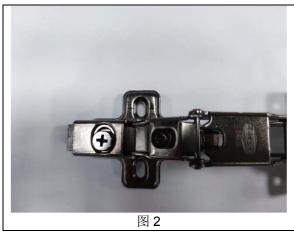







Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at http://www.sgs.com/en/Terms-and-Conditions.aspx and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention:To check the authenticity of testing / inspection report & certificate, please contact us at telephone:(86-755) 8307 1443, or email: CN.Doccheck@sgs.com

[146.767iiii] CN.Doccheck@sgs.com

[147.67aiiii] Chieck without believe beli

1作。「Building Europsen Industrial Part,Na.1 Sturthe South Read,Wisslas Section,Dallarg Tom,Sturde-Enstan,Guangdong,China 528333 t (86-757)22805888 f (86-757)22805888 www.sgsgroup.com.cn 中国・广东・佛山市原徳区大良街道办事处五沙順和南路1号欧洲工业园一号厂房首层 邮编:528333 t (86-757)22805888 f (86-757)22805888 e sgs.china@sgs.com




检测报告

编号: SDHL2206011762FT

日期:2022年07月05日

页码:第6页共6页

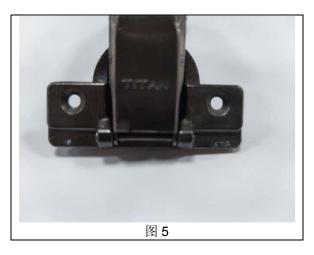

报告结束



1作。「Building Europsen Industrial Part,Na.1 Sturthe South Read,Wisslas Section,Dallarg Tom,Sturde-Enstan,Guangdong,China 528333 t (86-757)22805888 f (86-757)22805888 www.sgsgroup.com.cn 中国・广东・佛山市原徳区大良街道办事处五沙順和南路1号欧洲工业园一号厂房首层 邮编:528333 t (86-757)22805888 f (86-757)22805888 e sgs.china@sgs.com